



Note

## Isolation and Characterization of Alginic Acid from Commercially Cultured *Nemacystus decipiens* (Itomozuku)

Masakuni TAKO,<sup>†</sup> Seiki KIYUNA, Shuntoku UECHI, and Fujiya HONGO

Department of Bioscience and Biotechnology, Faculty of Agriculture, University of the Ryukyus, Nishihara, Okinawa 903-0123, Japan

Received July 19, 2000; Accepted October 30, 2000

An alginate was isolated from commercially cultured *Nemacystus decipiens* which had been harvested in Yonashiro Town (Okinawa, Japan). The yield of the alginate was 1.6% (w/w of wet alga), and the uronic acid, ash and moisture contents of the alginate were 86.0%, 12.0%, and 2.3% (w/w), respectively. The molecular mass of the alginate was estimated to be about  $1.5 \times 10^5$ . The infrared spectrum and optical rotation of the alginate were in agreement with those of the standard alginate. D-Mannuronic acid and L-guluronic acid were identified by <sup>1</sup>H- and <sup>13</sup>C-NMR spectroscopy, the molar ratio of both sugar residues being estimated to be 0.72:1.00.

**Key words:** alginic acid; Itomozuku; *Nemacystus decipiens*

Alginate is a major gelling carbohydrate polymer obtained from a number of brown seaweeds (Phaeophyceae) and is of considerable technological importance for both its solution properties and as a gelling agent.<sup>1)</sup> Alginate is a linear, (1→4)-linked copolymer of α-L-guluronate and β-D-mannuronate, the relative proportions of which, and their sequence within the primary structure, show substantial variations between species, and between different tissues within the same plant.<sup>2)</sup> We have proposed a gelation mechanism for alginate at the molecular level in an aqueous solution.<sup>3)</sup>

In the previous study,<sup>4)</sup> we isolated alginate which consisted of D-mannuronate and L-guluronate in a molar ratio of 0.27 to 1.00 from *Cladosiphon okamuranus* Tokida (Okinawamozuku) which had been commercially cultured on artificially seeded nets (1.5 × 20 m). The yield of alginate was estimated to be 0.1% (w/w) based on wet algae, while the acetyl fucoidan content was 2.3%. This suggested that fucoidan could be commercially produced on a simple industrial scale from artificially cultured Okinawamozuku. The annual production of this alga in Okinawa was reported to have been approximately

18,500 t in 1999.

*Nemacystus decipiens* Kuckuck (Itomozuku), one of the brown algae, is widespread on the shore between Akita and Okinawa Prefectures in Japan. In Okinawa Prefecture, the production of Itomozuku by artificially seeded culture nets has been carried out in the sea since 1979. The annual production of Itomozuku in Okinawa was reported to have been approximately 2,500 t in 1999. The seaweed is used together with Okinawamozuku in salad (Sunomono), so that their utilization by the food industry has been increasing. A fucoidan has recently been prepared on an industrial scale from Okinawamozuku and used as an additive to health foods and drinks in Japan.

We have previously isolated a fucoidan of about 0.5% in yield based on the wet seaweed from Itomozuku.<sup>5)</sup> However, an alginate of the spontaneous and artificially cultured alga has not previously been studied. We therefore report here the isolation and identification of an alginate from artificially cultured Itomozuku.

Itomozuku, which was commercially cultured on nets (1.5 × 20 m) in the sea off Yonashiro Town (Heanza Island, Okinawa) from November 1995 to May 1996, was used in this study. An alginate (45G, molar ratio of D-mannuronic acid to L-guluronic acid = 0.26:1.00; Kibun Food Chemipha Co., Japan) was used as the standard.

A wet seaweed sample (100 g) was homogenized with double its weight of 0.2 M HCl (200 g), stirred at room temperature for 2 h, centrifuged at 23,000 g for 20 min and filtered through Celite 545.<sup>4,5)</sup> The residual precipitate was washed with distilled water and then suspended in a 3.0% Na<sub>2</sub>CO<sub>3</sub> solution at room temperature for 3 h to extract the alginate. The extract was neutralized with 0.1 M HCl and then gelled by the addition of 2.0% CaCl<sub>2</sub>. The gelatinous precipitate was separated by centrifugation at 23,000 g for 20 min. This precipitate was washed with distilled water, and then dissolved in a 1.0 M NaOH solution. The resulting solution was filtered through

<sup>†</sup> To whom correspondence should be addressed. Fax: +81-98-895-8734

Presented at the Annual Meeting of the Japanese Society of Applied Glycoscience, October 1–3, 1997, Kobe, Japan

Celite 545 and then dialyzed overnight against distilled water. In the presence of NaCl (200 mg), ethanol (2 vols.) was added and the precipitate was dried *in vacuo*. The crude alginate (2.0 g) was dissolved in 300 ml of distilled water and passed through a column of Amberlite IR-120 ( $H^+$ ) to deionize it, before being then neutralized with 0.5 M NaOH. The solution was dialysed against distilled water and then freeze-dried.

Uronic acid of the alginate was determined by the carbazol-sulfuric acid method,<sup>6</sup> using D-mannuronic acid (Sigma Co., U.S.A). High-performance liquid chromatography (SCL-6B; Shimadzu Co., Japan) with a column of TSKgel G3000PWL (7.8 × 300 mm, Tosoh Co., Japan) was carried out to estimate the molecular mass. Pullulan P-20, P-100, and P-400 (Showa Denko Co., Japan) of Mw  $2.28 \times 10^4$ ,  $1.12 \times 10^5$  and  $4.05 \times 10^5$ , respectively, were used as molecular weight markers, detection being made with a refractive index detector. Infrared spectra (FT-IR) were recorded with an IR-8200 infrared spectrophotometer (Shimadzu Co., Kyoto, Japan) for a sample dispersed on KBr discs. Optical rotation was measured at 589 nm by a DIP-180 polarimeter (Jasco Co., Tokyo, Japan) for a 0.2% (w/v) solution.

$^1H$ - and  $^{13}C$ -NMR spectra were recorded by an FT-NMR spectrometer (JNM- $\alpha$ 500, JEOL Co., Tokyo, Japan) at 500.00 and 125.65 MHz. Alginate (2.0%) isolated from Itomozuku was dissolved in 4 ml of  $D_2O$ , and data were recorded at 80°C. The  $^1H$ - and  $^{13}C$ -NMR chemical shifts are expressed in parts per million (ppm) relative to the internal sodium 3-(trimethylsilyl)propionic-2,2,3,3- $d_4$  (TSP, 0.00 ppm).


The Itomozuku sample reached 20–30 cm long having a cylindrical axil, the thick part of which was about 1.5 mm in diameters with a sharp tip. The alginate was prepared and purified as already described. This alginate obtained from Itomozuku was a colorless fibrous powder in a yield of 1.6% (w/w; based on the wet alga). The uronic acid, ash, and moisture contents were 86.0%, 12.0%, and 2.3%, respectively (Table 1).

Liquid chromatography, using standard pullulan, gave a value of approximately  $1.5 \times 10^5$  for the molecular mass (Fig. 1). The infrared spectrum of the alginate isolated from Itomozuku was measured (not shown in Figure), the spectrum being in agreement with that of the standard alginate (45G). The optical rotation of the alginate showed a value of  $-0.103^\circ$  at a temperature of 50°C, then it increased a little with decreasing temperature, before showing a value of  $-0.098^\circ$  at 20°C. These values are in agreement with those of the standard alginate.

The  $^1H$  nuclear magnetic resonance (NMR) spectrum at 500 MHz of the alginate isolated from Itomozuku is shown in Fig. 2. Signal assignment of the alginate was achieved by the comparing with previously reported chemical shifts.<sup>7-9</sup> The spectrum


**Table 1.** Chemical Components of the Alginate Isolated from *Nemacystus decipiens*

Alginate	% (w/w)		
	Uronic acid	Ash	Moisture
Alginate	86.0	12.0	2.3

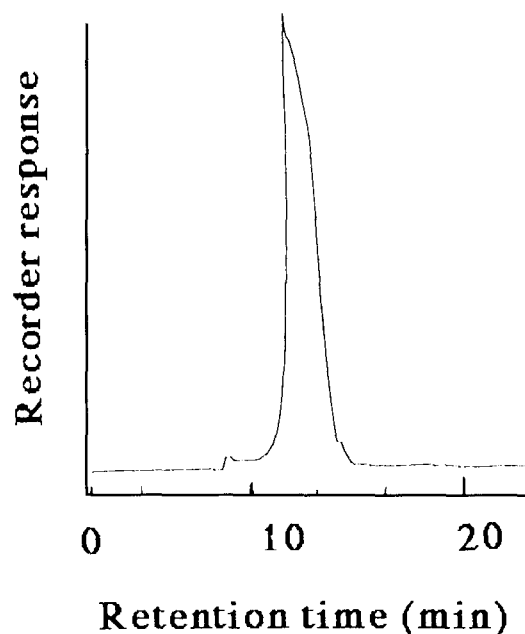


**Fig. 1.** Gel Filtration Chromatogram of Alginate Acid from Itomozuku.

Column, TSKgel G4000PWL (7.8 × 300 mm), eluent, 150 mM sodium chloride in a 50 mM phosphate buffer (pH 7.0); eluent flow, 0.5 ml/cm.

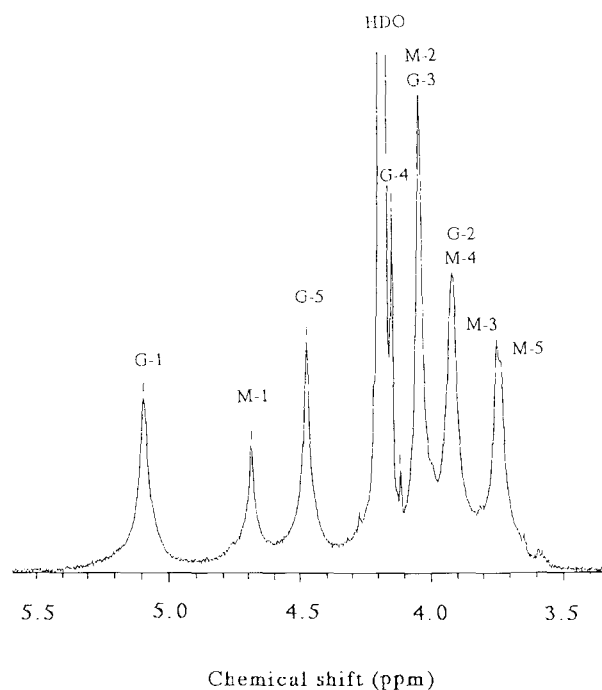

**Fig. 2.**  $^1H$ -NMR Spectrum of Alginate Acid from Itomozuku in  $D_2O$  at 80°C.

Abbreviations: M, D-mannuronic acid; G, L-guluronic acid.

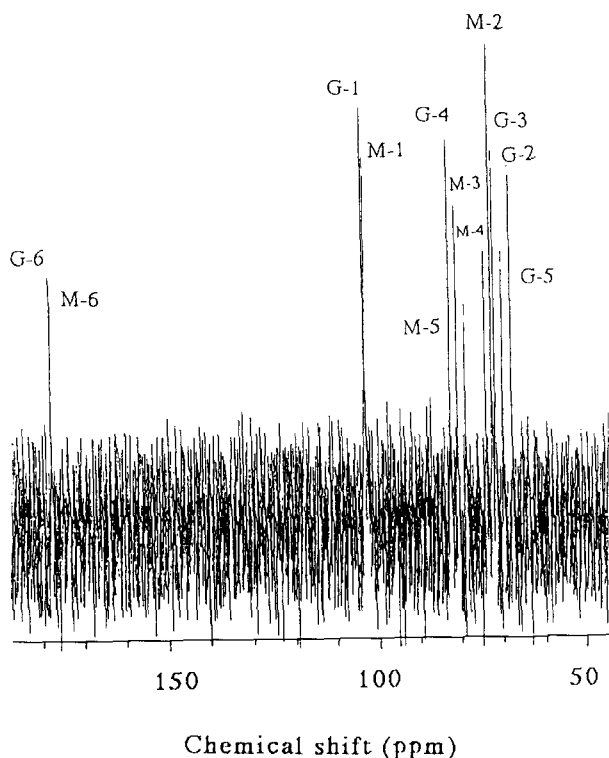

**Fig. 3.**  $^{13}\text{C}$ -NMR Spectrum of Alginic Acid from Itomozuku in  $\text{D}_2\text{O}$  at  $80^\circ\text{C}$ .  
Abbreviations: M, D-mannuronic acid; G, L-guluronic acid.

showed ten peaks (M1, 4.67; M2, 4.03; M3, 3.74; M4, 3.90; M5, 3.72; G1, 5.07; G2, 3.90; G3, 4.03; G4, 4.13; G5, 4.46 ppm). The chemical shifts are in agreement of those of the standard alginate (45G). The chemical shifts of the anomeric protons were assigned at 5.07 (L-guluronic acid) and 4.67 (D-mannuronic acid) ppm. The molar ratio of D-mannuronic acid to L-guluronic acid for the alginate was estimated from the signal area of both the anomeric protons to be 0.72:1.00.

As shown in Fig. 3, the  $^{13}\text{C}$ -NMR spectrum of the alginate from Itomozuku indicated twelve peaks. The  $^{13}\text{C}$ -NMR spectrum of the alginate had resolved chemical shifts in the carbonyl carbon region of 175.75 (G6) and 175.58 (M6) ppm,<sup>10,11</sup> in the anomeric region of 101.44 (G1) and 100.97 (M1) ppm, respectively, and of 66.04 (G2), 70.83 (M2), 70.01 (G3), 72.29 (M3), 60.71 (G4), 78.94 (M4), 68.18 (G5), 77.01 (M5) ppm. These data are consistent with those of the standard alginate (45G). The chemical shifts were assigned to the repeating unit of L-guluronic acid-rich alginate.<sup>12,13</sup> No any other chemical shift assigned to a carbon atom was evaluated.

Although Itomozuku is widespread between Akita and Okinawa Prefectures, the production of the alga has been decreased annually by an effect probably caused by sea pollution. However, the alga has been artificially cultured on a commercial scale off the Okinawa Islands since 1979. The optimum depth for

growth of the alga has been estimated to be 2 meters below the low-tide level. The harvest from the one sheet of a culture-net ( $1.5 \times 20.0$  m) of the alga is about 100 kg in wet weight.

Itomozuku contains a fucoidan of about 0.5% yield based on the wet seaweed.<sup>5</sup> This fucoidan consisting of L-fucose, D-galactose and sulfuric acid in the molar ratio of 1.0:0.1:1.0. Fucoidans seem to have such biological activities as anti-coagulant,<sup>14</sup> anti-thrombin,<sup>15</sup> anti-tumor<sup>16</sup> and anti-HIV<sup>17</sup> infection, because of the high number of substituting sulfate groups. Thus, fucoidan and alginate can be produced on an industrial scale from *Itomozuku* artificially cultured in Okinawa, Japan.

## References

- 1) Morris, E. R., Rees, D. A., Thom, D., and Boyd, J., Chiroptical and stoichiometric evidence of a specific primary dimerization in alginate gelation. *Carbohydr. Res.*, **66**, 145–154 (1978).
- 2) Naug, A., Larsen, B., and Smidsrod, O., Uronic acid sequence in alginate from different sources. *Carbohydr. Res.*, **32**, 217–225 (1974).
- 3) Tako, M. and Kohda, Y., Calcium induced association characteristics of alginate. *J. Appl. Glycosci.*, **44**, 153–159 (1997).
- 4) Tako, M., Yoza, E., and Tohma, S., Chemical characterization of acetyl fucoidan and alginate from commercially cultured *Cladosiphon okamuranus*. *Bot. Mar.*, **43**, 393–398 (2000).
- 5) Tako, M., Nakada, T., and Hongou, F., Chemical characterization of fucoidan from commercially cultured *Nemacystus decipiens* (Itomozuku). *Biosci. Biotechnol. Biochem.*, **63**, 1813–1815 (1999).
- 6) Galambos, J. T., The reaction of carbazole with carbohydrates. *Anal. Biochem.*, **19**, 119 (1967).
- 7) Grasdalen, H., Larsen, B., and Smidsrod, O., A P.M.R. study of the composition and sequence of uronate residues in alginates. *Carbohydr. Res.*, **68**, 23–31 (1979).
- 8) Grasdalen, H., High-field  $^1\text{H}$ -N.M.R. spectroscopy of alginate sequential structure and linkage conformations. *Carbohydr. Res.*, **118**, 255–260 (1983).
- 9) Steiginsky, C. A., Beale, J. M., Floss, H. G., and Mayer, R. M., Structural determination of alginic acid and the effects of calcium binding as determined by high-field N.M.R. *Carbohydr. Res.*, **225**, 11–26 (1992).
- 10) Grasdalen, H., Larsen, B., and Smidsrod, O.,  $^{13}\text{C}$ -N.M.R. studies of alginate. *Carbohydr. Res.*, **56**, C-11–C-15 (1977).
- 11) Grasdalen, S., Larsen, S., and Smidsrod, O.,  $^{13}\text{C}$ -N.M.R. studies of monomeric composition and sequence in alginate. *Carbohydr. Res.*, **89**, 179–191 (1981).
- 12) Panikkar, R. and Brasch, D., Composition and block structure of alginates from New Zealand brown seaweeds. *Carbohydr. Res.*, **293**, 119–132 (1997).
- 13) Heyarand, A., Gey, C., Leonard, C., Rochas, C., Girond, S., and Kloareg, B., NMR spectroscopic analysis of oligoguluronates and oligomannuronates

- prepared by acid or enzymic hydrolysis of homopolymeric blocks of alginic acid. *Carbohydr. Res.*, **289**, 11–16 (1996).
- 14) Collic, S., Fischer, A. M., Tapon-Brethaudiere, J., Boisson, C., Durand, P., and Jozefonicz, J., Anticoagulant properties of a fucoidan fraction. *Thrombosis Res.*, **64**, 143–154 (1991).
  - 15) Nishino, T. and Nagumo, T., The relationship between the sulfate content and the antithrombin activity of an  $\alpha$ -(1→2)-fucoidan purified from a commercial fucoidan fraction. *Bot. Mar.*, **38**, 187–193 (1995).
  - 16) Itoh, H., Amano, H., Zhuang, H., and Mizuno, T., Antitumor activity and immunological properties of marine algal polysaccharides, especially fucoidan, prepared from *Sargassum Thumbergii* of phaeophyceae. *Anticancer Res.*, **13**, 2045–2052 (1993).
  - 17) McClure, M. C., Whitby, D., Patience, C., Gooderham, N. J., Bradshaw, A., Cheingsong-Popov, R., Weber, J. N., Davies, D. S., Cook, G. M. W., Keynes, R. J., and Weiss, R. A., Dextransulfate and fucoidan are potent inhibitors of HIV infection *in vitro*. *Antiviral Chem. Chemotherapy*, **2**, 149–156 (1999).